

# Pressure dependence of ferroelectric quantum critical fluctuations: tuning the soft phonon mode in strontium titanate

M.J. Coak,<sup>1,2,3,4</sup> C.R.S. Haines,<sup>1,5</sup> C. Liu,<sup>1,5</sup> G. G. Guzmán-Verri,<sup>1,6</sup> and S.S. Saxena<sup>1,7</sup>

<sup>1</sup>*Cavendish Laboratory, Cambridge University, J.J. Thomson Ave, Cambridge CB3 0HE, UK*

<sup>2</sup>*Center for Correlated Electron Systems, Institute for Basic Science, Seoul 08826, Republic of Korea*

<sup>3</sup>*Department of Physics and Astronomy, Seoul National University, Seoul 08826, Republic of Korea*

<sup>4</sup>*Department of Physics, University of Warwick, Coventry CV4 7AL, UK*

<sup>5</sup>*CamCool Research Ltd. 44 Thornton Close, Girton, Cambridge, CB3 0NG, UK*

<sup>6</sup>*Centro de Investigación en Ciencia e Ingeniería de Materiales (CICIMA) and Escuela de Física, Universidad de Costa Rica, San José, Costa Rica 11501*

<sup>7</sup>*National University of Science and Technology “MISIS”, Leninsky Prospekt 4, Moscow 119049, Russia*

(Dated: 25th April 2019)

The effect of quantum critical ferroelectric fluctuations on the temperature dependent dielectric constant of SrTiO<sub>3</sub> has been long studied and continues to yield great insight into the mechanisms of quantum criticality. The effect of those same fluctuations on the pressure and temperature dependence of the ferroelectric soft phonon mode as the system is tuned away from criticality are reported for the first time in this paper. We show that the mean field approximation is confirmed experimentally. Furthermore, using a self-consistent model of the quantum critical excitations including coupling to the volume strain and without adjustable parameters, we determine that the corrections to mean field behavior are logarithmic and would only be observed very close to the quantum critical point. Thus, the mean-field character of the pressure dependence is much more robust to the fluctuations than is the temperature dependence. Stronger corrections are predicted for lower dimensionalities - we briefly discuss the pressure dependence of quantum critical fluctuations in uniaxial and XY ferroelectrics. The same calculation confirms that the Lydanne-Sachs-Teller relation is valid over the whole pressure and temperature range considered. Therefore, the measured dielectric constant can be used to extract the frequency of the soft mode down to 1.5 K and up to 20 kbar of applied pressure. The frequencies are then compared to those measured in quantum paraelectric KTaO<sub>3</sub> and shown to correspond at around 2 kbar. The soft mode is observed to stiffen further, raising the low-temperature energy gap and returning towards the expected shallow temperature dependence of an optical mode. This behavior is consistent with the existence of a ferroelectric quantum critical point on the pressure-temperature phase diagram of SrTiO<sub>3</sub>, which applied pressure tunes the system away from. This work represents the first experimental measurement of the stiffening of a soft phonon mode as a system is tuned away from criticality, a potentially universal phenomenon across a variety of phase transitions and systems in condensed matter physics.

## I. INTRODUCTION

The incipient ferroelectric SrTiO<sub>3</sub> has been studied in great detail and is used as a dielectric or an insulating substrate in many applications [?] as it possess an anomalously high dielectric constant at low temperatures. SrTiO<sub>3</sub> is the clearest example of a quantum paraelectric known. The nature of the quantum paraelectric state has been an open question since Barrett [?] first attempted to describe the deviation from Curie-Weiss behavior observed in SrTiO<sub>3</sub>. Recently, progress has been made [?] in describing this state but the effect of fluctuations on the pressure dependence has not been considered until this work.

SrTiO<sub>3</sub> has a cubic perovskite structure at room temperature, but a well-documented antiferrodistortive transition occurs at around 110 K [?], below which the unit cell is tetragonal, extended along the c-axis. The dielectric constant,  $\epsilon_r$ , of SrTiO<sub>3</sub> exhibits a classical Curie-Weiss temperature dependence at high temperatures [?], but departs from the Curie-Weiss behavior as the polarization is modified by quantum fluctuations be-

low 50 K, and no ferroelectric ordering is observed. The displacive ferroelectric transition the classical fit would imply results from the ionic motion of a transverse optical phonon mode, which softens to approach zero energy at low temperature at the zone center  $\Gamma$  point. This mode, commonly described as the ‘soft mode’ or ‘ferroelectric mode’ corresponds to opposing motion of the oxygen octahedra and titanium ions along the c-axis [?]. Inelastic neutron scattering experiments by Yamada et.al. [?] have shown however that the soft mode is ‘frozen out’ at low temperatures - instead of falling to zero the phonon energy flattens out to a fixed value or gap  $\Delta$  as temperature is decreased below 50 K. This means that spontaneous long-range ferroelectricity does not form, but a low-energy excitation into short range charge ordering is available to the system, leading to the very large polarizability and departures from classical predictions seen at low temperatures [?]. These phenomena have been linked to a postulated ferroelectric quantum critical point (QCP) at the equivalent of a small ‘negative pressure’ on SrTiO<sub>3</sub>’s pressure-temperature phase diagram (Fig. 1) - quantum critical fluctuations of the polarization in the

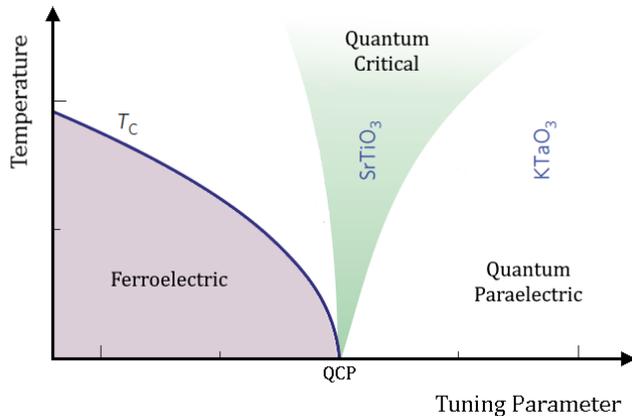


Figure 1. Predicted phase diagram for SrTiO<sub>3</sub> and related compounds [? ]. The ‘tuning parameter’ can be realized through either chemical doping or substitution, or by applying pressure to tune the frequencies of the phonon oscillators. SrTiO<sub>3</sub> sits naturally slightly to the right of a quantum critical point on this diagram, and pressure serves to push it further away from the quantum critical region and towards the behavior of KTaO<sub>3</sub>.

vicinity of this point lead to a modified dependence of the dielectric properties. The application of strain [? ], or the substitution of a heavier oxygen isotope to form SrTi<sup>18</sup>O<sub>3</sub> [? ? ], which both have the opposite effect on the system to applying pressure, lead to a ferroelectric phase, consistent with this QCP. Our recent work [? ] has shown through detailed measurements of the dielectric constant under pressure that SrTiO<sub>3</sub> is driven away from its quantum critical regime by the application of pressure. The dielectric response was in addition seen to match that seen in KTaO<sub>3</sub> at elevated pressures, in agreement with the position on the pressure/doping phase diagram postulated for this material (Fig. 1).

Critical exponents in the temperature dependence of susceptibility, resistivity and heat capacity have been used extensively to identify and characterize the various states discovered in the heavy fermion systems and incipient transition metal itinerant magnets [? ]. There are good reasons for this. In particular the power of the temperature critical exponents lies in the incredible precision that temperature can be controlled and measured. This is not in general true for pressure. There are also differences in how pressure and temperature affect the energy scales - for the temperature case, the quantum critical cone is extremely narrow at low  $T$  and then widens out, with subtle exponent crossovers, and with quantum critical effects persisting to unintuitively high temperatures. In contrast, a small change in pressure at low temperature - where critical effects are strongest just above the QCP - can push the system out of the quantum critical cone. It is worth understanding why the pressure dependence is mean-field-like - widely assumed but by no

means obvious from first principles.

In this study the pressure dependence is measured explicitly. The relative paucity of data points compared to the temperature sweeps prohibits detailed numerical analysis. However by extending the self-consistent phonon model of [? ? ] to include a coupling of the soft optical phonon to the volume strain we show that, with the exception of a narrow region very close to the QCP, the pressure dependence is indeed mean-field-like. As a consequence of this, whilst the crossovers from quantum critical to classical and quantum paraelectric are clear in the temperature exponents, this crossover does not appear in the pressure dependence.

However, by considering a standard microscopic model of the ferroelectric fluctuations coupled to the volume strain and solved within the self-consistent phonon approximation (SCPA) [? ? ], we reveal that the pressure dependence is indeed mean-field-like except very near the QCP where weak logarithmic corrections are expected. The SCPA is equivalent to the self-consistent renormalization method used for itinerant magnets [? ].

The accompanying changes to the soft mode frequency have not been studied with pressure and temperature, and are reported here for the first time, extracted from the temperature and pressure dependence of the dielectric constant. The Lydanne-Sachs-Teller (LST) relation [? ] allows the dielectric response of a polarizable crystal to be determined from its phonon spectrum or vice versa. The full relation including all phonon branches can be written as

$$\frac{\epsilon_r}{\epsilon_\infty} = \frac{\prod_i \omega_{iLO}^2}{\prod_i \omega_{iTO}^2}, \quad (1)$$

where  $\epsilon_r$  denotes the relative permittivity of the material,  $\epsilon_\infty = n$  the refractive index or dielectric response at frequencies well above the relevant phonon frequencies and  $\omega_{iLO}^2$  and  $\omega_{iTO}^2$  are the frequencies of the longitudinal optical (LO) and transverse optical (TO) of phonon mode  $i$  at the zone center ( $q = 0$ ). In SrTiO<sub>3</sub> a single TO mode corresponding to opposite motions of the titanium ion and surrounding oxygen octahedron is softened at the zone center [? ] and dominates the dielectric properties of the system. Following Barker [? ] and Yamada [? ], we simplify the LST relation by assuming the pressure and temperature dependence of all modes other than the soft TO and its accompanying LO mode to be insignificant. Over the 20 kbar (2 GPa) range reported in this study, SrTiO<sub>3</sub> does not undergo any structural transitions, changes in lattice parameters are well under a percent [? ] and the variation of room-temperature phonon frequencies has been shown to be linear with pressure up to a much larger range [? ]. The effect of these comparatively low pressures (several orders of magnitude below the bulk modulus [? ]) on SrTiO<sub>3</sub> is therefore to cause a small leading-order perturbation to the lattice and phonons, with the notable exception of the soft mode. All

other optical modes can be expected to tune with applied pressure in the same manner, and their terms in the LST relation cancel, leading to

$$\frac{\epsilon_r}{\epsilon_\infty} = \frac{\omega_{LO}^2}{\omega_{TO}^2}, \quad (2)$$

where  $\omega_{TO}$  and  $\omega_{LO}$  denote the ferroelectric soft mode and its longitudinal equivalent, which is denoted as  $E_g$  and of energy  $148 \text{ cm}^{-1}$  by Ishidate et.al. [? ].

## II. EXPERIMENTS

### A. Methods

High precision capacitance measurements were carried out on single crystal samples of SrTiO<sub>3</sub> from Crystal GmbH with gold electrodes vacuum evaporated onto the surfaces in a parallel-plate capacitor geometry. Measurements under extremely hydrostatic pressure conditions were made possible by the development, in collaboration with CamCool Research Ltd, of a piston-cylinder clamp cell with miniature shielded coaxial cables running into the sample region and electrically isolated from the cell body. This eliminates stray capacitances from the wiring and allows pF capacitance signals to be measured with stabilities of one part in a million. The shield conductors of the coaxial cables were joined together at the sample position and at the measurement instrument in the standard 2-point capacitance setup. The pressures in the measurements reported were 0/ambient, 2.4, 3.3, 4.6, 5.2, 6.9, 8.6, 9.6, 11.9, 14.1, 15.7, 17.1, 18.6 and 20.0 kbar, with a typical uncertainty of  $\pm 0.2$  kbar. An Andeen-Hagerling 2550A 1 kHz capacitance bridge was used, at a voltage of 0.1 V. Sample thickness, corresponding to capacitor plate separation, was 0.5 mm. Measurements were taken on a modified 1K Dipper cryostat from ICE Oxford, allowing continuous stable temperature control down to 1.2 K, and an adiabatic demagnetization refrigerator developed in house capable of reaching 200 mK. Typical heating or cooling rates were held at 0.01 K per minute to allow the large thermal mass of the pressure cell to thermally equilibrate.

### B. Results

Measurements were carried out of the dielectric constant of SrTiO<sub>3</sub> from room temperature down to 1.5 K at fixed hydrostatic pressures up to 20.0 kbar. The effect of pressure, as discussed in more detail in our recent paper [? ], is to drastically reduce the magnitude of the low-temperature dielectric constant from  $\sim 18,000$  at ambient pressure to  $\sim 500$  at 20.0 kbar as the system is tuned away from a ferroelectric transition and associated quantum critical behavior.

Such a drastic change in the dielectric properties must reflect a change in the phonon spectrum of the system as the two are linked by the LST - the phonon frequencies directly determine the dielectric response. Eq. 2 was used to extract the temperature and pressure dependence of the frequency  $\omega_{TO}$  of the ferroelectric soft mode  $\omega_{TO}^2 = \frac{\epsilon_\infty \omega_{LO}^2}{\epsilon_r}$  at the zone centre.  $\epsilon_\infty$  and  $\omega_{LO}$  only change by  $\sim 1\%$  over the pressure and temperature ranges studied, as will be shown in the rest of this section, so a good approximation of  $\omega_{TO}$  can be found by simply setting these to be constant. Including the known pressure and temperature dependencies of these parameters will give a more accurate estimate of the phonon frequency however, and this was done to find the data presented in Fig. 2(a).

The refractive index at high frequencies  $\epsilon_\infty$  was assumed to be temperature independent, in line with the conclusions of Kamarás et al. [? ], but the pressure,  $p$ , dependence was considered. The linear pressure dependence with a value of  $\left. \frac{d\epsilon_\infty}{dp} \right|_{300 \text{ K}} = -1.43 \times 10^{-4} \text{ kbar}^{-1}$  found by Giardini [? ] for optical frequencies at room temperature was used to model the changes in  $\epsilon_\infty$ . An exact numerical value for  $\epsilon_\infty$  is hard to define, as  $n$  exhibits frequency dependence out to the highest frequencies measured [? ? ], but can be estimated as between 2.7 - 3.0 under ambient conditions. The numerical value for  $\epsilon_\infty(p=0)$  was therefore set to 2.87 by fitting the extracted phonon frequencies at ambient pressure to the experimental values found by Yamada et.al. [? ] from inelastic neutron scattering.

The longitudinal optical mode frequency  $\omega_{LO}$  has been found to be  $150 \text{ cm}^{-1} = 18.6 \text{ meV}$  under ambient conditions by Ishidate et al. [? ] and Lebedev [? ]. Ishidate measured room temperature phonon frequencies in SrTiO<sub>3</sub> up to a pressure range an order of magnitude higher than that reported in this work, and found a linear pressure dependence throughout, with  $\left. \frac{d\omega_{LO}}{dp} \right|_{300 \text{ K}} = 1.8 \text{ cm}^{-1} \text{ GPa}^{-1} = 0.0223 \text{ meV kbar}^{-1}$ . The temperature variation of  $\omega_{LO}$  at ambient pressure was reported by Servoin et.al. [? ], and this was fitted with a linear relationship to extract a gradient  $\left. \frac{d\omega_{LO}}{dT} \right|_{p=0} = 0.0066 \text{ cm}^{-1} \text{ K}^{-1} = 0.00082 \text{ meV K}^{-1}$ . Both pressure and temperature effects are therefore on order a percent over the ranges studied, just as with the refractive index changes, so all three must be considered for a rigorous analysis.

Holding  $\omega_{LO}$  and  $\epsilon_\infty$  constant as in Yamada et.al. and fitting the resulting constant of proportionality to match the Yamada data gives  $\omega_{TO}^2 = \frac{39204}{\epsilon_r}$ , with frequencies  $\omega$  in meV and  $\epsilon_r = \epsilon/\epsilon_0$  dimensionless. Yamada had a similar conversion factor of 37790, suggesting comparable sample quality - the dielectric constant is very sensitive to sample purity and surface finish, easily explaining the slight difference. Including the variation in  $\omega_{LO}$  and  $\epsilon_\infty$

a)

Figure 2. a) Zone-center soft mode phonon energy of SrTiO<sub>3</sub> extracted from the dielectric constant via the Lydanne-Sachs-Teller relation, plotted against temperature for applied pressures from ambient (blue, lowest) to 20 kbar (red, topmost). The variation of the frequencies of other phonon branches and the refractive index with temperature and pressure were modeled as described in the text. Neutron scattering data from Yamada et al. [?] are shown as open circles and the corresponding data for KTaO<sub>3</sub> from Shirane et. al. [?] as crosses. b) Calculated temperature dependence of the TO phonon energy for several pressures.

b)

leads to:

$$\omega_{TO}^2 = \frac{(2\pi)^2}{\epsilon_r} \left[ 2.87 - \frac{p}{6993} \right] \left[ 18.6 + \frac{p}{44.8} + \frac{(T - 300)}{1220} \right],$$

(pressures in kbar, temperature in K) which was used to extract the values for  $\omega_{TO}$  shown in Fig. 2(a) As pressure is increased the phonon frequency markedly flattens off and returns towards the flat temperature dependence of an archetypal optical mode. The low-temperature gap,  $\Delta$ , is doubled from 2 meV by even 2.4 kbar, the smallest pressure applicable with this setup. The small phonon energy or gap is directly linked to the ferroelectric quantum critical fluctuations observed in this material, so the gap widening as seen and becoming energetically inaccessible as the system is tuned away from criticality is an expected result. The prediction that pressure will tune the system towards the behavior seen in KTaO<sub>3</sub> is supported by the data as well - the soft mode energy for KTaO<sub>3</sub> overlayed on Fig. 2(a) lie by inspection at where SrTiO<sub>3</sub> values at around 2 kbar would be found.

Fig. 3(a) shows the pressure dependence of  $\omega_{TO}$  at fixed temperatures, taken directly from the data of Fig. 2(a). The data at 1.5 K, 2 K, 5 K and those extrapolated to 0 K all overlap as the dielectric response flattens off as temperature approaches zero, so any data in this range can be taken as the zero-temperature value. The inset of Fig. 3(a) shows the square of the phonon energy at 2 K, equivalent to the zero-temperature gap,  $\Delta$ , plotted against pressure. This shows very good agreement to a linear fit, giving the behavior expected from Landau theory  $\omega = \omega_0(p - p_c)^{0.5}$  with the critical pressure  $p_c$  at which the ferroelectric quantum critical point occurs equal to -0.7(1) kbar. This is in agreement with the analysis in our earlier paper [?] and with observations that strain or oxygen-18 substitution (both equivalent to ‘negative pressure’ in SrTiO<sub>3</sub>) drive the system to a ferroelectric state [? ? ?].

### III. THEORY

#### A. Model

We consider a standard model Hamiltonian for displacive ferroelectrics with normal mode coordinates that describe local displacements  $\phi_{i\alpha}$ , with  $\alpha = 1, 2, \dots, n = d$  in the unit cell  $i = 1, 2, \dots, N$  that are associated with the

soft TO mode, the condensation of which is driven by the dipolar force and leads to the ferroelectric transition. We also consider the coupling to volume strain  $\eta_i$ . The Hamiltonian is as follows, [?]

$$H = H_\phi + H_\eta + H_{\phi\eta}, \quad (3)$$

where  $H_\phi$  is the Hamiltonian of the polar degrees of freedom alone,

$$H_\phi = \frac{1}{2} \sum_{i,\alpha} \Pi_{i\alpha}^2 + \frac{\omega_0^2}{2} \sum_{i,\alpha} \phi_{i\alpha}^2 + \sum_{i,\alpha\beta} [u + v\delta_{\alpha\beta}] \phi_{i\alpha}^2 \phi_{i\beta}^2 + \frac{1}{2} \sum_{ij,\alpha\beta} F_{\alpha\beta} (i - j) \phi_{i\alpha} \phi_{j\beta},$$

$H_\eta$  is the elastic energy,

$$H_\eta = \frac{K}{2} \sum_i \eta_i^2 + P \sum_i \eta_i,$$

and  $H_{\phi\eta}$  is a linear-quadratic coupling between  $\phi_{i\alpha}$  and  $\eta_i$ ,

$$H_{\phi\eta} = -\lambda \sum_{i,\alpha} \eta_i \phi_{i\alpha}^2.$$

Here,  $\Pi_{i\alpha}$  is the conjugate momentum of  $\phi_{i\alpha}$ ; and  $F_{\alpha\beta} (i - j)$  is the dipolar interaction with Fourier transform  $F_{\alpha\beta}(\mathbf{q}) = q^2 \delta_{\alpha\beta} + g_0 q_\alpha q_\beta / q^2$ , where  $g_0$  is a constant that depends on the lattice structure.  $\omega_0$  is the frequency of the purely harmonic model;  $u$  and  $v$  are coefficients of the isotropic and anisotropic cubic anharmonicities, respectively;  $\lambda$  is the coupling constant between the polarization and volume strain; and  $K$  and  $P$  are, respectively, the bulk modulus and applied hydrostatic stress (e.g. biaxial stress for  $d = 2$  and pressure for  $d = 3$ ).

Though the low temperature paraelectric lattice structure of SrTiO<sub>3</sub> is tetragonal, we will assume cubic symmetry for simplicity [?]. The TO excitations of (3) are thus doubly degenerate,

$$\Omega_{\mathbf{q}}^2 = r(T, P) + q^2, \quad (4)$$

where  $r(T, P) \equiv \Delta^2(T, P)$  is the square of the phonon gap at the zone-center. In addition to (4), there is a singlet LO mode which we will neglect as it is gapped out by the large depolarizing field of order  $\mathcal{O}(g)$ . Within the SCPA, [? ?]  $r(T, P)$  is given as follows,

$$r(T, P) = \omega_0^2 + [4(d + 2)u + 12v] \langle |\phi|^2 \rangle - 2\lambda \langle \eta \rangle, \quad (5)$$

a)

Figure 3. a) Zone-center soft mode phonon energy of SrTiO<sub>3</sub>, plotted against pressure at fixed temperatures. The solid lines show fits to  $\omega_0(p - p_c)^{0.5}$  with  $\omega_0$  and  $p_c$  free fitting parameters to guide the eye. The inset gives the square of the zero-temperature extrapolated phonon gap,  $\Delta$ , against pressure, with a linear fit shown as a solid line. b) Calculated pressure dependence of the TO phonon energy for several temperatures. Inset. Calculated pressure dependence of the TO phonon gap.

b)

where  $\langle |\phi|^2 \rangle$  are the fluctuations of polarization,

$$\langle |\phi|^2 \rangle = \frac{1}{N} \sum_{\mathbf{q}} \frac{1}{\Omega_{\mathbf{q}}} \left[ n(\Omega_{\mathbf{q}}/k_B T) + \frac{1}{2} \right], \quad (6)$$

with  $n(x) = (e^x - 1)^{-1}$  a Bose factor and  $\langle \eta \rangle$  is the average volume strain,

$$\langle \eta \rangle = \frac{\lambda}{K} \langle |\phi|^2 \rangle - \frac{P}{K}. \quad (7)$$

By substituting Eqs. (6) and (7) into Eq. (5), we separate the contributions from thermal and quantum fluctuations as follows [? ],

$$r(T, P) = \frac{2\lambda}{K} (P - P_c) + \Gamma \left\{ (T/T_D)^{d-1} \Phi \left[ r(T, P) / (k_B T)^2 \right] + Z_0[r(0, P)] - Z_0[0] \right\}, \quad (8)$$

where  $P_c$  is the critical pressure at  $T = 0$  K,

$$\frac{2\lambda}{K} P_c = -[r(0, 0) + \Gamma \{Z_0[0] - Z_0[r(0, 0)]\}], \quad (9)$$

and,

$$\Phi[R] = \frac{(k_B T_D)^{d-1}}{(2\pi)^d} \times \int_0^{T_D/T} dx x^{d-1} \frac{1}{\sqrt{R+x^2}} n(\sqrt{R+x^2}), \quad (10a)$$

$$Z_0(r) = \frac{(k_B T_D)^{d-1}}{2(2\pi)^d} \int_0^1 dx x^{d-1} \frac{1}{\sqrt{r/(k_B T_D)^2 + x^2}}, \quad (10b)$$

where  $r(0, 0) = \omega_0^2 + \Gamma Z_0[r(0, 0)]$ ,  $\Gamma = 4(d+2)u + 12v - 2\lambda^2/K$ , and  $T_D = \Lambda/k_B$  is the Debye temperature. Eqs. (8), (9), and (10) self-consistently determine the temperature and pressure dependence of  $r(T, P)$ .

## B. Results

The non-adjustable model parameters are  $\omega_0, \Gamma, \lambda, K$ , and  $\Lambda$  which we fit experimental data reported for SrTiO<sub>3</sub> as follows:  $\omega_0$  and  $\Gamma$  are determined from the temperature dependence of the transverse optic phonon gap measured by neutron scattering, [? ];  $\lambda$  is obtained from

the slope of  $\Delta^2$  versus  $P$  measured here (see inset of Fig. 3(b)); and  $\Lambda$  from specific heat data ( $T_D = \Lambda/k_B = 400$  K) [? ]. The resulting parameters are  $\omega_0 = 9.6i$  meV,  $\Gamma = 80.0$  meV<sup>3</sup>,  $\lambda/K = 0.054$  meV<sup>2</sup>, and  $\Lambda = 34.5$  meV. The calculated temperature and pressure dependence of  $r(T, P)$  is in good qualitative and quantitative agreement with experiments, as shown in Figs. 2 and 3.

To further explore the behavior of the excitations, we study the pressure dependence of the fluctuations near the QCP. At  $T = 0$  K, Eq. (8) gives,

$$r(0, P) = \frac{2\lambda}{K} (P - P_c) + \Gamma \{Z_0[r(0, P)] - Z_0[0]\}. \quad (11)$$

For  $r \rightarrow 0$ ,

$$Z_0[r] - Z_0[0] \simeq \begin{cases} -b \ln r + cr, & d = 1, \\ -br^{1/2} + cr, & d = 2, \\ -br + cr \ln r, & d = 3, \\ -br + cr^{3/2}, & d = 4, \end{cases} \quad (12)$$

with  $b, c$  positive constants. Thus the lower (upper) critical dimension is  $d_{lc} = 1$  ( $d_{uc} = 4$ ). While there are strong deviations from mean field behavior for  $d = 2$ , the corrections are only logarithmic for  $d = 3$ . Equation. (11) then gives,

$$r(0, P) \propto \begin{cases} (P - P_c)^2, & d = 2, \\ (P - P_c), & d \geq 3, \end{cases} \quad (13)$$

with weak logarithmic corrections for  $d = 3$ . Such corrections should be observable only when extremely close to the QCP ( $|(P - P_c)/P_c| \ll 1$ ) and a renormalization group analysis would be required for a quantitative description. For the present experiments,  $|(P - P_c)/P_c| \gtrsim 1$ , and thus are not observable.

Quantum critical excitations in uniaxial and XY ferroelectrics are generally expected to differ from those of cubic systems. We consider such cases in Appendix A.

## IV. CONCLUSIONS

By treating the pressure within a self-consistent phonon theory of the kind used to successfully account for the thermal exponents observed in quantum critical SrTiO<sub>3</sub> we show that the pressure dependence is robustly mean-field like. There are logarithmic corrections at very close to absolute zero but these extend only to very low pressures (much less than 1 kbar). At the same time

we verify the applicability of the LST over the whole of the phase space considered. The experimentally observed evolution of the phonon energies provides the first measurement of the stiffening of a soft phonon mode as a system is tuned away from criticality - a potentially universal and important result.

The Lydanne-Sachs-Teller relation was used to extract the pressure and temperature dependence of the transverse optical soft mode frequency in SrTiO<sub>3</sub> from precision measurements of the dielectric constant under pressure. The mode was seen to stiffen as pressure was applied, moving towards a more typical flat optical mode. The low-temperature phonon gap  $\Delta$  widened with increasing pressure, showing excellent agreement to the  $\Delta \propto (p - p_c)^{0.5}$  predicted by Landau theory and with an extrapolated critical pressure  $p_c$  of -0.7(1) kbar, matching the position of the quantum critical point predicted in our previous paper [? ].

The evolution of the ferroelectric soft mode in SrTiO<sub>3</sub> with pressure, the natural tuning parameter to directly address the phonon spectrum, has been determined and shown to support the assertion that SrTiO<sub>3</sub> is an incipient ferroelectric and can be tuned away from a ferroelectric quantum critical point by the application of pressure. Pressure causes a drastic change in the temperature dependence of the soft mode.

SrTiO<sub>3</sub> forms an ideal model system for the study of the physics of soft phonon modes and of quantum criticality, and pressure allows direct and clean tuning of the phonons - the driving mechanism of the whole system.

## ACKNOWLEDGEMENTS

The authors would like to thank G.G. Lonzarich, P.B. Littlewood, F.M. Grosche, D.E. Khmel'nitskii, S.E. Dutton, N.D. Mathur, J. van Wezel, G. Tsironis, C. Panagopoulos, L.J. Spalek, H. Hamidov, P.A.C. Brown, D. Jarvis and J. Zaanen for their help and discussions.

We would also like to acknowledge support from Jesus, Churchill and Trinity Colleges of the University of Cambridge, the Engineering and Physical Sciences Research Council, IHT KAZATOMPROM and the CHT programme. The work was carried out with financial support from the Ministry of Education and Science of the Russian Federation in the framework of Increase Competitiveness Program of NUST MISiS (№ K2-2017-024), implemented by a governmental decree dated 16th of March 2013, N 211. Work at the University of Costa Rica is supported by the Vice-rectory for Research under the project no. 816-B7-601 and the Office of International Affairs.

## Appendix A: Uniaxial and XY ferroelectrics

For uniaxial ferroelectrics, there is an preferred polarization direction which we choose to be the  $x_3$ -axis. The Hamiltonian is similar to that of Eq. (3) except that  $\alpha = \beta = 3, v = 0$ , and  $F(\mathbf{q}) = \frac{q^2 + g(q_3/q)^2}{q^2}$ . The phonon excitations are  $\Omega_{\mathbf{q}} = \sqrt{r + q^2 + g(q_3/q)^2}$ , [? ] which give

$$Z_0[r] - Z_0[0] = \begin{cases} br + cr \ln r + \mathcal{O}(r^2), & d = 2, \\ br + \mathcal{O}(r^{3/2}), & d = 3. \end{cases} \quad (\text{A1})$$

The upper critical dimension is thus  $d_{uc} = 3$  and there are weak logarithmic corrections in  $d = 2$ .

For XY ferroelectrics, there is an easy plane of polarization and the Hamiltonian is again similar to that of Eq. (3) except that  $\alpha = \beta = 1, 2$ . The excitations are  $\Omega_{\mathbf{q}} = \sqrt{r + q^2}$  and  $\Omega_{\mathbf{q}} = \sqrt{r + q^2 + g(q_1^2 + q_2^2)/q^2}$ . The former isotropic dispersion dominates the critical behavior and the corrections to mean-field behavior are thus the same as those given in Eq. (12).